




## R270.70

EN:  
Type: 446



R270.70 is a heat resistant high chromium nonhardenable ferritic stainless steel well suited for service in temp up to 1095°C (2000°F) for applications requiring excellent resistance to oxidation but where strength and toughness are not prime factors. The risk of 475°C (880°F) embrittlement and precipitation of sigma phase that appear in high Cr-steel must always be taken into consideration. Typical applications are muffer packings, oil burner components, furnace parts and wire for glass sealing.

### CHEMICAL COMPOSITION (Nominal) %

C	Si	Mn	Cr	Ni	Mo	N	Al	
0.050	0.50	1.00	23.9	<0.50	<0.50	0.085	0.020	

PRE: 26 (PRE = Cr + 3.1 x Mo + 25 x N)

Comments:

### PHYSICAL PROPERTIES

Condition: Annealed


Density	7.7 g / cm <sup>3</sup>
Modulus of elasticity, E	225 000 GPa
Specific heat 0-100°C	500 J / kg°C

### TYPICAL MECHANICAL PROPERTIES

Condition: D-cooled

Proof strength	Rp0.2	min.300 N / mm <sup>2</sup>
Tensile strength	Rm	500-580 N / mm <sup>2</sup>
Elongation	A10	min.25 %

### DEFORMATION GRAPH

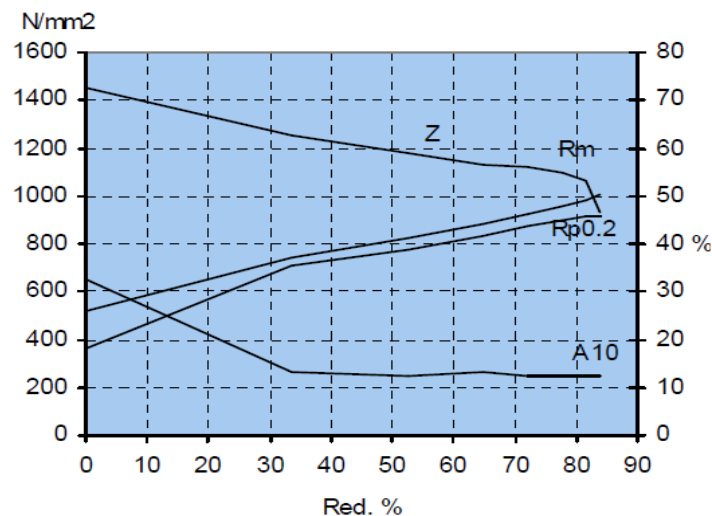

### THERMAL TREATMENT

Annealing temperature	800-850 °C
	1470-1560 °F

### MAX. OPERATING TEMPERATURE

Operating temp. in air	1095 °C
	2000 °F
Scaling temp. in air	1095 °C
	2000 °F

### THERMAL CONDUCTIVITY

20 °C	21.0 W / mK
100 °C	21.5 W / mK
200 °C	22.0 W / mK
400 °C	23.5 W / mK

### THERMAL EXPANSION

Thermal expansion per °C x 10<sup>-6</sup> from 20°C to:

100 °C	10.0
200 °C	10.5
400 °C	11.5
600 °C	12.0
800 °C	12.0
1000 °C	13.5

### RESISTIVITY

20 °C	750 μΩmm
100 °C	800 μΩmm
200 °C	900 μΩmm
400 °C	1150 μΩmm
600 °C	1200 μΩmm
800 °C	1250 μΩmm